

Method to analyze programmable deformation of dielectric elastomer layers

Xuanhe Zhao and Zhigang Suo^{a)}

School of Engineering and Applied Sciences, Harvard University, Cambridge, Massachusetts 02138, USA

(Received 5 November 2008; accepted 28 November 2008; published online 22 December 2008)

A layer of a dielectric elastomer expands its area when a voltage is applied across its thickness. The layer can be programmed to deform in three dimensions by using patterned prestretches, electrodes, and stiffeners. To aid the design of such programmable deformation, this paper describes a computational method, exploiting the fact that the prescribed voltage sets the nominal electric field. The method is demonstrated with examples including formation of wrinkles, movements of a handlike actuator, and nonlinear oscillation of a balloon. © 2008 American Institute of Physics. [DOI: 10.1063/1.3054159]

Intense effort is being made to develop dielectric elastomers for applications such as sensors, actuators, and generators.^{1–3} The essential part of such a device is a layer of a dielectric elastomer sandwiched between two compliant electrodes. When a voltage is applied between the electrodes, the layer reduces its thickness and expands its area. For the layer to deform appreciably, the electric field needed is high, on the order of 10^8 V/m. To avoid excessively high voltage in use, the layer must be thin, typically below 1 mm.

Programmable deformation in three dimensions can be achieved with patterned prestretches, electrodes, and stiffeners.^{1–3} Existing computational methods, however, have only been demonstrated for relatively simple configurations.^{4–11} This paper describes a method that can be embedded in a commercial finite element software. Consequently, the method can be widely used to explore dielectric elastomer devices of complicated configurations and functions.

Our method is based on a general theory of elastic dielectrics.^{12–17} The synopsis here closely follows Ref. 17. When an elastic dielectric deforms from a reference state to a current state at time t , a material particle of coordinate \mathbf{X} in the reference state moves to a place of coordinate $\mathbf{x}(\mathbf{X}, t)$ in the current state. The deformation gradient is

$$F_{iK} = \frac{\partial x_i(\mathbf{X}, t)}{\partial X_K}. \quad (1)$$

The nominal electric field is

$$\tilde{E}_K = - \frac{\partial \Phi(\mathbf{X}, t)}{\partial X_K}, \quad (2)$$

where $\Phi(\mathbf{X}, t)$ is the electrical potential of the material particle \mathbf{X} in the current state.

Let $\mathbf{B}(\mathbf{X}, t)dV(\mathbf{X})$ be the applied force on an element of volume, $\mathbf{T}(\mathbf{X}, t)dA(\mathbf{X})$ the applied force on an element of surface, $\rho(\mathbf{X})dV(\mathbf{X})$ the mass of the element of volume, $Q(\mathbf{X}, t)dV(\mathbf{X})$ the charge on the element of volume, and $\Omega(\mathbf{X}, t)dA(\mathbf{X})$ the charge on the element of surface. The elastic dielectric is held at a fixed temperature, so that the thermodynamic state of an element of volume is characterized by

a free-energy function, $\hat{W}(\mathbf{F}, \tilde{\mathbf{E}})$. Every element of the body is in a state of local thermodynamic equilibrium if

$$\int \frac{\partial \hat{W}}{\partial F_{iK}} \frac{\partial \xi_i}{\partial X_K} dV = \int \left(B_i - \rho \frac{\partial^2 x_i}{\partial t^2} \right) \xi_i dV + \int T_i \xi_i dA \quad (3)$$

holds for arbitrary function $\xi_i(\mathbf{X})$ and if

$$\int \frac{\partial \hat{W}}{\partial \tilde{E}_K} \frac{\partial \zeta}{\partial X_K} dV = \int Q \zeta dV + \int \Omega \zeta dA \quad (4)$$

holds for arbitrary function $\zeta(\mathbf{X})$. The integrals extend over the volume and surface of the body, respectively.

Equations (1)–(4) define an initial-value problem that yields the fields $\mathbf{x}(\mathbf{X}, t)$ and $\Phi(\mathbf{X}, t)$. The following data need to be prescribed: the fields of displacement, velocity, and electric potential at an initial time, the applied forces $\mathbf{B}(\mathbf{X}, t)$ and $\mathbf{T}(\mathbf{X}, t)$, the electric charges $Q(\mathbf{X}, t)$ and $\Omega(\mathbf{X}, t)$, the mass density $\rho(\mathbf{X})$, and the free-energy function $\hat{W}(\mathbf{F}, \tilde{\mathbf{E}})$. Also prescribed are the displacement and voltage on parts of the boundary.

We now specialize the general theory to a form suitable for thin layers. The layer is taken to be free of extrinsic charges, so that $Q=0$ everywhere and $\Omega=0$ on the surfaces of the layer uncovered by electrodes. More than one pair of electrodes may be patterned on the layer in order to program complex sequences of deformation. The lateral size of each electrode is large compared to the thickness of the layer, such that the fringe field at the edges of the electrodes can be neglected so far as the overall deformation is concerned. The electric field can also be neglected in part of the layer uncovered by the electrodes. The nominal electric field in the layer between a pair of electrodes is

$$\tilde{\mathbf{E}} = \frac{\Phi}{H} \mathbf{N}, \quad (5)$$

where Φ is the voltage applied between the electrodes in the current state, H is the thickness of the layer in the reference state, and \mathbf{N} is the unit vector normal to the layer in the reference state. The direction of \mathbf{N} is fixed if the layer in the reference state is planar but varies if the layer in the reference state is curved. In both cases, the prescribed voltage sets the nominal electric field.

^{a)}Electronic mail: suo@seas.harvard.edu.

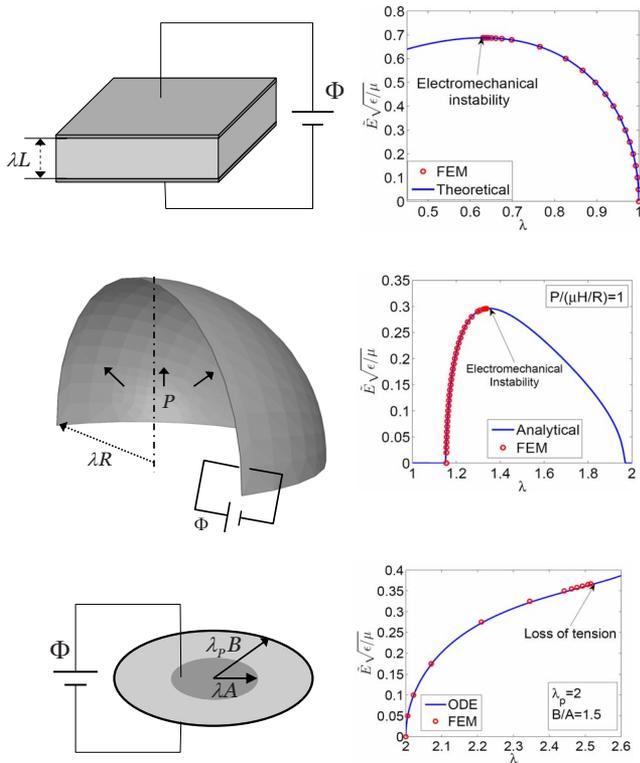


FIG. 1. (Color online) Several simple configurations: a flat layer fully covered by electrodes on both faces, a spherical balloon subject to a pressure and a voltage, and a prestretched flat layer partially covered by circular electrodes.

For the layer Eq. (2) is replaced by Eq. (5) to prescribe the nominal electric field, and Eq. (4) is removed from the list of governing equations. Consequently, Eqs. (1) and (3) define the initial-value problem that yields the field $\mathbf{x}(\mathbf{X}, t)$. The structure of this initial-value problem is identical to that of an elastic body subject to mechanical loads alone. The known nominal electric field [Eq. (5)] enters the problem through the free-energy function $\hat{W}(\mathbf{F}, \tilde{\mathbf{E}})$ in a form of an eigenstrain.

We embed this method in the commercial finite element software, ABAQUS, by coding the free-energy function $\hat{W}(\mathbf{F}, \tilde{\mathbf{E}})$ and its derivatives in a user-supplied subroutine, UMAT. To illustrate the method, we adopt a model material, called the ideal dielectric elastomer, with the free-energy function,¹⁸

$$\hat{W}(\mathbf{F}, \tilde{\mathbf{E}}) = \frac{\mu}{2} [F_{iK} F_{iK} - 2 \log(\det \mathbf{F}) - 3] + K(\det \mathbf{F} - 1)^2 - \frac{\varepsilon F_{iK}^{-1} \tilde{E}_K F_{iL}^{-1} \tilde{E}_L}{2 \det \mathbf{F}}, \tag{6}$$

where μ is the shear modulus and ε is the permittivity. Following a usual practice in computation, we use the second term to approximately enforce incompressibility of the elastomer, with the constant K set to be much greater than μ .¹⁰

We verify our method by analyzing several simple configurations (Fig. 1), which have been analyzed by solving algebraic equations or ordinary differential equations (ODEs).^{11,14,19,20} For a flat layer of an elastomer fully covered by electrodes on both faces, the deformation in the layer is homogenous until the nominal electric field reaches a

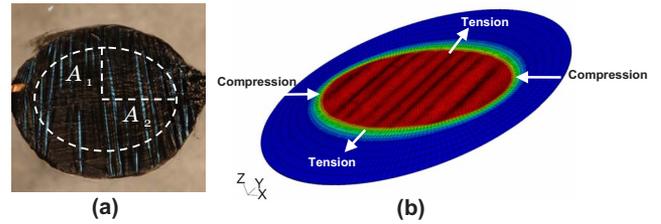


FIG. 2. (Color online) A prestretched layer partially covered by elliptic electrodes. Wrinkles form when the voltage exceeds a critical value (Ref. 21).

peak, where the layer undergoes the electromechanical instability.¹¹ When we use the static option in this calculation, the method reproduces the analytic solution before the instability but does not go beyond the instability. The situation is similar for the balloon subject to a pressure and a voltage.¹⁴ For a flat layer partially covered by circular electrodes and prestretched, our method reproduces the existing results obtained by the ODE (Ref. 6) and goes beyond the existing results when the layer loses tension, as discussed below.

When the voltage-induced expansion in area is constrained by surrounding materials, the layer may form wrinkles; Fig. 2(a) shows an example.²¹ We model a layer patterned with elliptic electrodes, the ratio of the two axes being $A_1/A_2=0.6$. The layer is prestretched by $\lambda_p=1.1$ and is then subject to a voltage. As the voltage increases, the region with electrodes expands in all directions. The stress in the direction of axis A_2 becomes compressive, while the stress in the direction of A_1 is still tensile. Wrinkles form along the A_2 direction, Fig. 2(b). Our method may be used to examine the effects of wrinkles on the operation of the devices.

A handlike actuator has been demonstrated recently.⁹ A prestretched layer of a dielectric elastomer is first attached to a frame cut from a thin foil of a polymer. When the external constraint is removed, this planar structure self-assembles into a three-dimensional shape. The structure opens when a voltage is applied across the thickness of the elastomer and closes when the voltage is withdrawn. The structure can be

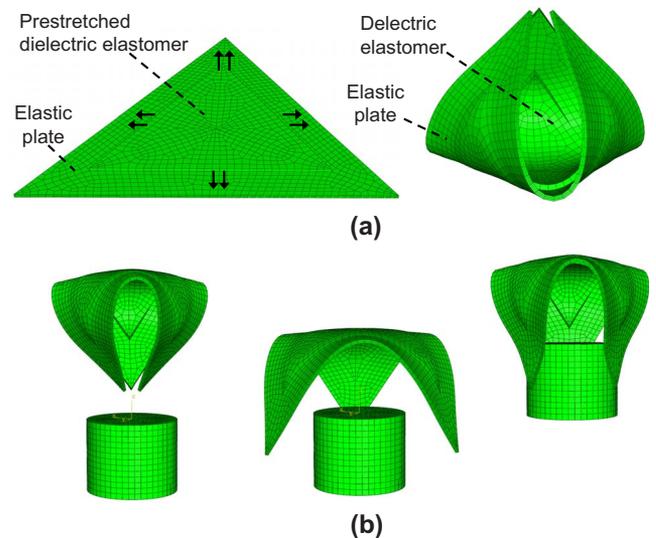


FIG. 3. (Color online) A handlike actuator (Ref. 9). The thickness of the frame is set to be equal to that of the dielectric elastomer, and the shear modulus of the frame is set to be twice that of the dielectric elastomer.

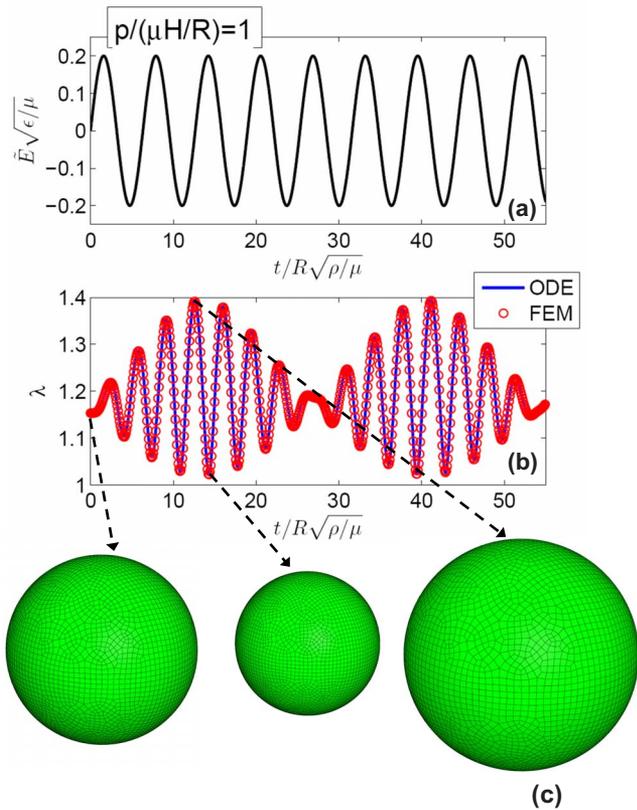


FIG. 4. (Color online) Nonlinear oscillation of a balloon subject to a sinusoidal voltage and a constant pressure.

used to pick and place objects. Figure 3(a) shows the simulation of the self-assembly from a planar structure to a three-dimensional one. We also simulate the structure as it opens, closes, and lifts a weight by contact friction, Fig. 3(b).

Once an oscillating voltage is applied across the skin of a pressurized balloon, the balloon oscillates. The oscillation is nonlinear when the amplitude of the voltage is large enough, as shown in a previous study using an ODE.²² We use this phenomenon to illustrate the capability of simulating dynamic deformation. Figure 4(a) shows the applied oscillating voltage, and Fig. 4(b) shows the simulated oscillation of the balloon. The balloon oscillates with the same frequency as the input voltage. The amplitude of the oscillation, how-

ever, varies with another frequency. The results from our simulation match perfectly with those from solving the ODE.

In summary, we have developed a method to simulate programmable deformation of dielectric elastomer layers. Our method, embedded in a commercial finite element software, can be widely used to explore devices of complicated configurations and functions.

This work is supported by the U.S. Army Research Office through a MURI grant on electrets and by DARPA through a project on programmable matter. X.Z. acknowledges the support of the Founder's Prize, through the American Academy of Mechanics, sponsored by the Robert M. and Mary Haythornthwaite Foundation. We thank the authors of Ref. 21 for providing Fig. 2(a).

¹F. Carpi, D. De Rossi, R. Kornbluh, R. Pelrine, and P. Sommer-Larsen, *Dielectric Elastomers as Electromechanical Transducers* (Elsevier, Oxford, 2008).

²A. O'Halloran, F. O'Malley, and P. McHugh, *J. Appl. Phys.* **104**, 071101 (2008).

³Y. Bar-Cohen and Q. M. Zhang, *MRS Bull.* **33**, 173 (2008).

⁴F. Carpi and D. De Rossi, *Mater. Sci. Eng., C* **24**, 555 (2004).

⁵M. I. Frecker and W. M. Aguilera, *Smart Mater. Struct.* **13**, 82 (2004).

⁶J. S. Plante and S. Dubowsky, *Int. J. Solids Struct.* **43**, 7727 (2006).

⁷M. Wissler and E. Mazza, *Sens. Actuators, A* **120**, 184 (2005).

⁸D. K. Vu, P. Steinmann, and G. Possart, *Int. J. Numer. Methods Eng.* **70**, 685 (2007).

⁹G. Kofod, W. Wirges, M. Pajajnen, and S. Bauer, *Appl. Phys. Lett.* **90**, 081916 (2007).

¹⁰J. X. Zhou, W. Hong, X. H. Zhao, Z. Q. Zhang, and Z. G. Suo, *Int. J. Solids Struct.* **45**, 3739 (2008).

¹¹X. H. Zhao and Z. G. Suo, *Appl. Phys. Lett.* **91**, 061921 (2007).

¹²R. A. Toupin, *J. Acoust. Soc. Am.* **5**, 849 (1956).

¹³H. F. Tiersten, *J. Acoust. Soc. Am.* **57**, 660 (1975).

¹⁴N. Goulbourne, E. Mockensturm, and M. Frecker, *J. Appl. Mech.* **72**, 899 (2005).

¹⁵A. Dorfmann and R. W. Ogden, *J. Elast.* **82**, 99 (2006).

¹⁶R. M. McMeeking and C. M. Landis, *J. Appl. Mech.* **72**, 581 (2005).

¹⁷Z. G. Suo, X. H. Zhao, and W. H. Greene, *J. Mech. Phys. Solids* **56**, 467 (2008).

¹⁸X. H. Zhao, W. Hong, and Z. G. Suo, *Phys. Rev. B* **76**, 134113 (2007).

¹⁹R. Pelrine, R. Kornbluh, Q. B. Pei, and J. Joseph, *Science* **287**, 836 (2000).

²⁰J. W. Fox and N. C. Goulbourne, *J. Mech. Phys. Solids* **56**, 2669 (2008).

²¹C. Keplinger, M. Kaltenbrunner, N. Arnold, and S. Bauer, *Appl. Phys. Lett.* **92**, 192903 (2008).

²²J. Zhu, S. Q. Cai, and Z. G. Suo (unpublished).